arXiv:1109.0610v2 [cond-mat.mes-hall] 2 Jan 2012

Measurement of heavy-hole spin dephasing in (InGa)As quantum dots

R. Dahbashi,[1] J. Hübner,[1] F. Berski,[1] J. Wiegand,[1] X. Marie,[2] K. Pierz,[3] H. W. Schumacher,[3] and M. Oestreich[1]

[1] *Institute for Solid State Physics, Leibniz Universität Hannover, Appelstr. 2, D-30167 Hannover, Germany*
[2] *Université de Toulouse; INSA, UPS, CNRS; LPCNO,*
135 avenue de Rangueil, F-31077 Toulouse, France
[3] *Physikalisch Technische Bundesanstalt, Bundesallee 100, D-38116 Braunschweig, Germany*

(Dated: January 4, 2012)

We measure the spin dephasing of holes localized in self-assembled (InGa)As quantum dots by spin noise spectroscopy. The localized holes show a distinct hyperfine interaction with the nuclear spin bath despite the p-type symmetry of the valence band states. The experiments reveal a short spin relaxation time τ^{hh}_{fast} of 27 ns and a second, long spin relaxation time τ^{hh}_{slow} which exceeds the latter by more than one order of magnitude. The two times are attributed to heavy hole spins aligned perpendicular and parallel to the stochastic nuclear magnetic field. Intensity dependent measurements and numerical simulations reveal that the long relaxation time is still obscured by light absorption, despite low laser intensity and large detuning. Off-resonant light absorption causes a suppression of the spin noise signal due to the creation of a second hole entailing a vanishing hole spin polarization.

PACS numbers: 72.70.+m, 72.25.Rb,78.67.Hc, 85.75.-d

The spin of heavy-holes in quantum dots is carefully examined as a possible candidate for qubit implementation in solid-state based quantum information devices and has seen a large increase in research in recent years. Measurements on In(Ga)As/GaAs quantum dot (QD) ensembles yield hole spin dephasing times at zero external magnetic field of tens of nanoseconds.[1] Calculations show that these rather short hole spin relaxation times result from strain induced dipole-dipole interaction with the nuclei and that much longer heavy-hole (HH) spin relaxation times in Ising-type nuclear-spin interacting systems are finally limited by single hole-acoustic-phonon scattering and two-phonon processes.[2] The strength of the hole-hyperfine interaction has been extracted from pump-probe and time-resolved photoluminescence and resonance fluorescence experiments whereat the pump-probe experiments demonstrate the quenching of the hole-spin relaxation by an external longitudinal magnetic field which exceeds the effective nuclear field.[1, 3] Further experiments on single In(Ga)As/GaAs QDs show optical initialization of hole spins by optical pumping and highly coherent hole spins in coherent population trapping.[4, 5]

All the above experiments are based on different kinds of setups with significant perturbations of the QD system. In this letter, we demonstrate spin noise spectroscopy (SNS) as an alternative low perturbation and in principle quantum mechanical non-demolition experiment [6–8] to study the interaction of localized heavy holes with the surrounding nuclear spin bath in dependence on external longitudinal and transverse magnetic fields. Spin noise spectroscopy has been used on QD ensembles once before, however, mainly to study the anisotropy of the heavy hole g-factor.[9] In the following we apply magnetic fields at oblique angle with respect to the projection direction (z) of our all optical spin sensitive probing technique. The effective magnetic field given by the superposition of the stochastic nuclear and the applied external magnetic field divides the spin dynamics into a longitudinal and transverse component. The projection of both components onto the detection direction yields simultaneous access to the complete spin dynamic.

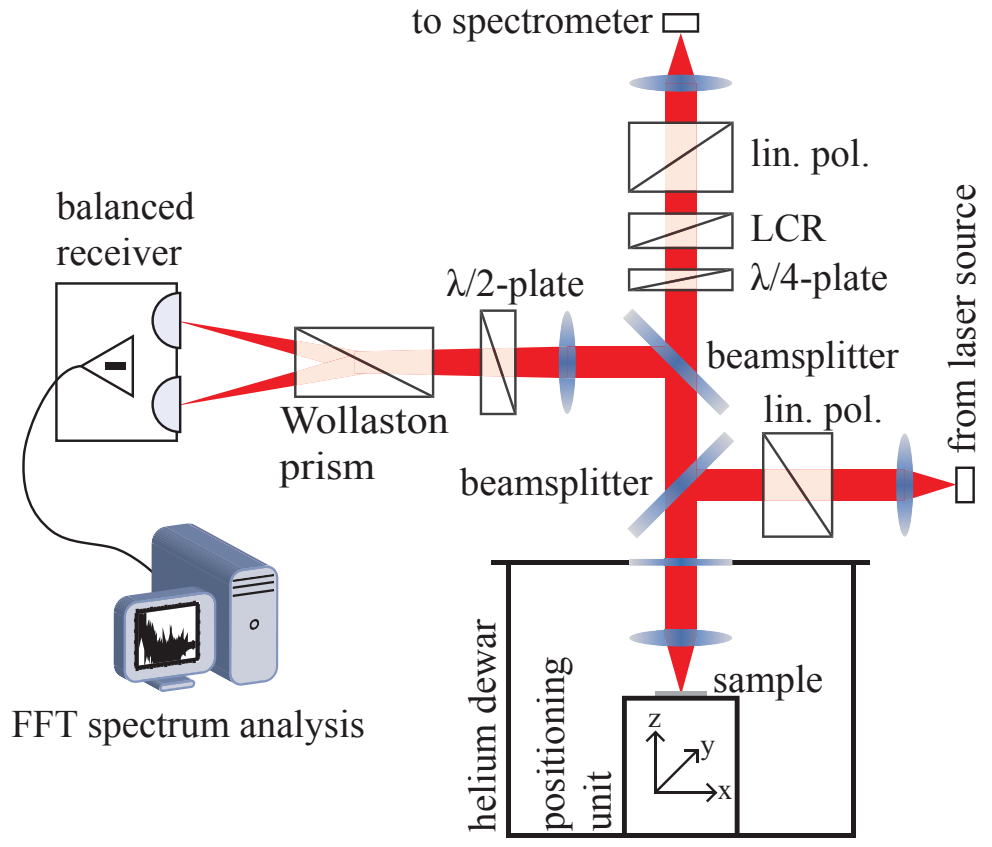

FIG. 1: (Color online) Experimental setup.

Spin noise spectroscopy utilizes in general the statistical fluctuations of a spin polarization at thermal equilibrium which contain according to the fluctuation-dissipation theorem the full temporal dynamics of the spin system under infinitesimal external perturbation. The spin fluctuation is recorded via non-resonant Faraday rotation of a linearly polarized probe laser. Figure 1 shows the corresponding experimental setup. The light source is a commercial low noise, tunable diode laser in Littman configuration. The linearly polarized laser light is focused to a beam waist of about 1 μm on the sample which is mounted in a free beam confocal microscope in a liquid Helium dewar at a constant temperature of 4.2 K. The sample is a single layer of InAs/GaAs quantum dots grown by molecular beam epitaxy on (100)-

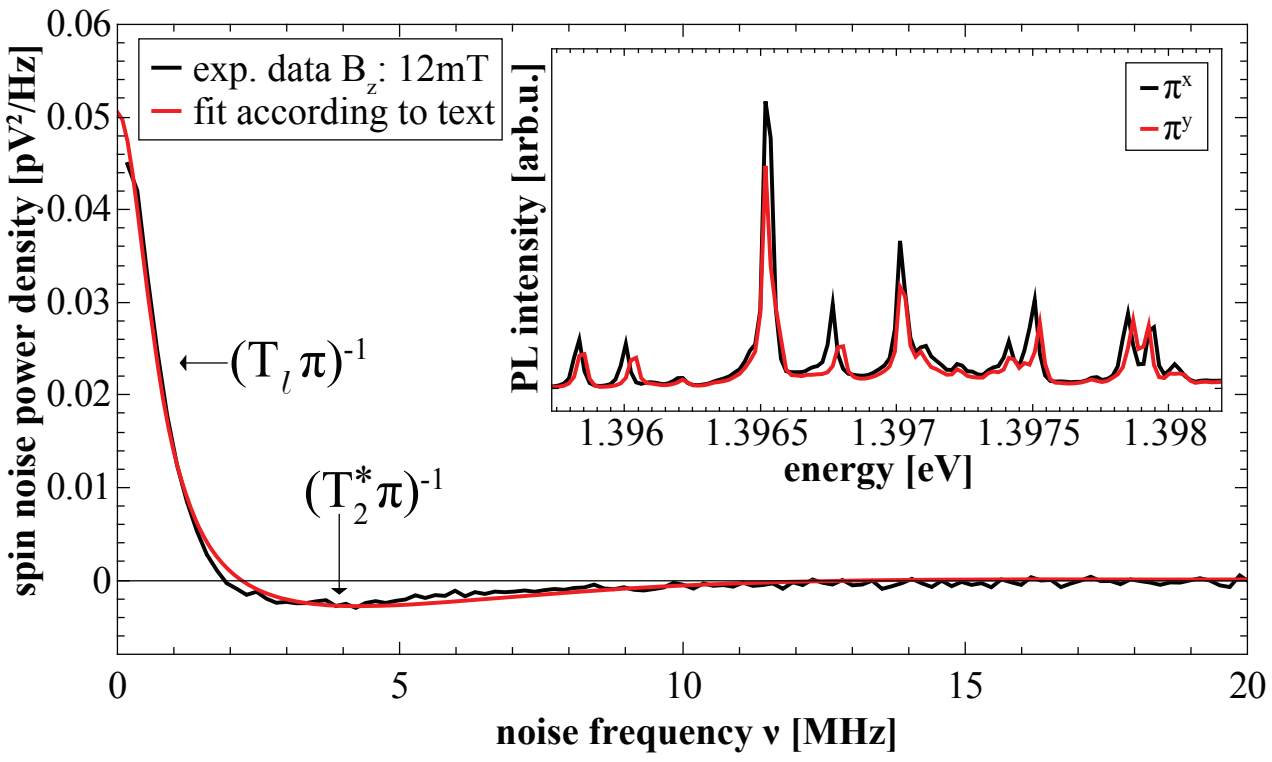

FIG. 2: (Color online) Typical spin noise difference spectrum (black line) at an excitation intensity of 140 μW/μm^2 and the corresponding fit (red curve) with one Lorentzian and one Gaussian curve centered at zero frequency. (Inset) Polarization resolved QD PL spectrum measured in growth direction.

oriented GaAs inside the antinode of a λ-Bragg cavity with 13 and 30 GaAs/AlAs layers for the top and bottom mirror, respectively. The high finesse microcavity enables SNS measurements in reflection and enhances the Faraday rotation noise signal without increasing the optical shot noise. The QD density varies spatially from zero to about 100 dots/μm^2 and some of these QDs are filled by a single hole due to the MBE p-type background of typically 10^{14} holes/cm^3. We choose for our SNS measurement a sample region with high dot density to increase the signal to noise ratio and to ensure that each QD is occupied in average by less than one hole from the background doping. Magnetic fields of up to 30 mT are applied both in Faraday and Voigt geometry. The spin induced stochastic Faraday rotation of the linear polarization of the reflected laser light is resolved outside the He dewar by a combination of a Wollaston prism and an 80 MHz low noise balanced photo receiver. The detected electrical signal is amplified by a low noise amplifier, digitized with 180 MHz sampling rate in the time domain, and Fourier transformed in real time. The noise background due to optical shot noise of the laser and electrical noise of the balanced receiver and the amplifier is eliminated by subtracting spin noise spectra with and without applied external magnetic field from each other.[8] This method works well due to the strong influence of the magnetic field on the spin noise spectra.

First, we characterize the sample by polarization resolved photoluminescence (PL) measurements. The inset of Fig. 2 shows the measured PL for excitation and detection in growth direction. The measured PL line width of individual QDs of 40 μeV is limited by the resolution of the spectrometer. Statistics over many sample spots show that about half of the measured QDs do not show an anisotropic exchange interaction splitting which is a good indication that these QDs are charged.[10] We observe QD PL in the growth direction only within the spectral width of the cavity resonance of 2.4 meV. Measurements from the side of the sample with a larger laser spot yield a QD PL width of 30 meV and we estimate accordingly that about 50 charged QDs are located within our 1 μm laser spot.

Next, we measure spin noise (SN) at the identical sample position as the depicted micro PL. Figure 2 shows an exemplary SN spectrum at $B_z^{ext} = 12$ mT minus a SN spectrum at $B_z^{ext} = 0$ mT where z is the growth direction and the direction of laser propagation. The laser wavelength has been red-detuned for this SN measurement from the closest charged QD resonance by approximately 20 times the full width at half maximum (FWHM) of the QD ground state transition. We do not observe a significant dependence of the SN spectrum on laser detuning which indicates that we indeed measure the spatio-spectral average of the QD ensemble in the laser focus.

The SN spectrum in Fig. 2 is fitted by one Lorentzian and one Gaussian curve, both centered at zero frequency. The fitting analysis reveals that the areas of the two curves are in very good approximation equal but have opposite signs. This is reasonable since the integrated spin noise power does not depend on magnetic field and the opposite sign results from calculating a difference spectrum. The fitting analysis yields a spectral ν_{FWHM} of 1.5 MHz for the Lorentzian curve ($B_z^{ext} = 12$ mT) and 11.9 MHz for the Gaussian curve ($B_z^{ext} = 0$ mT). The two ν_{FWHM} translate by $\nu_{\mathrm{FWHM}} = 1/(\pi\tau^{hh}_{fast,slow})$ [11] to hole spin relaxation times $\tau^{hh}_{slow} = 215$ ns and $\tau^{hh}_{fast} = 27$ ns, respectively. The spin relaxation time of 27 ns results from the transverse stochastic nuclear spin orientation in the QDs. The statistical nuclear spin fluctuations yield for the holes an effective nuclear field B^N_{hh} due to dipole-dipole interaction and τ^{hh}_{fast} is the corresponding QD HH spin transverse T_2^* time, i.e., describes the spin dynamics of the HH spin components which are perpendicular to B^N_{hh}. The T_2^* time translates with a HH g-factor of 0.15 [9] to $B^N_{hh} \approx 6$ mT which is in excellent agreement with pump-probe experiments on very similar ensembles of p-doped InAs-QDs and theory.[1] The excellent agreement confirms that our QDs are in fact occupied by heavy-holes. We can exclude loading of the QD with two holes since spin noise vanishes if both, the HH spin-up and spin-down, states are occupied. We can also exclude loading by a single electron since electron spin relaxation times in InAs-QDs are shorter by one order of magnitude at $B_z^{ext} = 0$ mT due to the much more efficient hyperfine interaction.

Figure 3 depicts the dependence of the SN spectrum on a longitudinal magnetic field in more detail. The measurement clearly shows that the spectrally broad $B_z^{ext} = 0$ mT, T_2^* spin noise power is gradually transferred with increasing B_z^{ext} into the narrow, longitudinal SN peak. This transfer of spin noise power and the width and amplitude of the narrow peak saturate for $B_z^{ext} \gg B^N_{hh}$.

We have also studied at $B_z^{ext} = 0$ mT the spin relaxation time of HH spins pointing along the stochastic

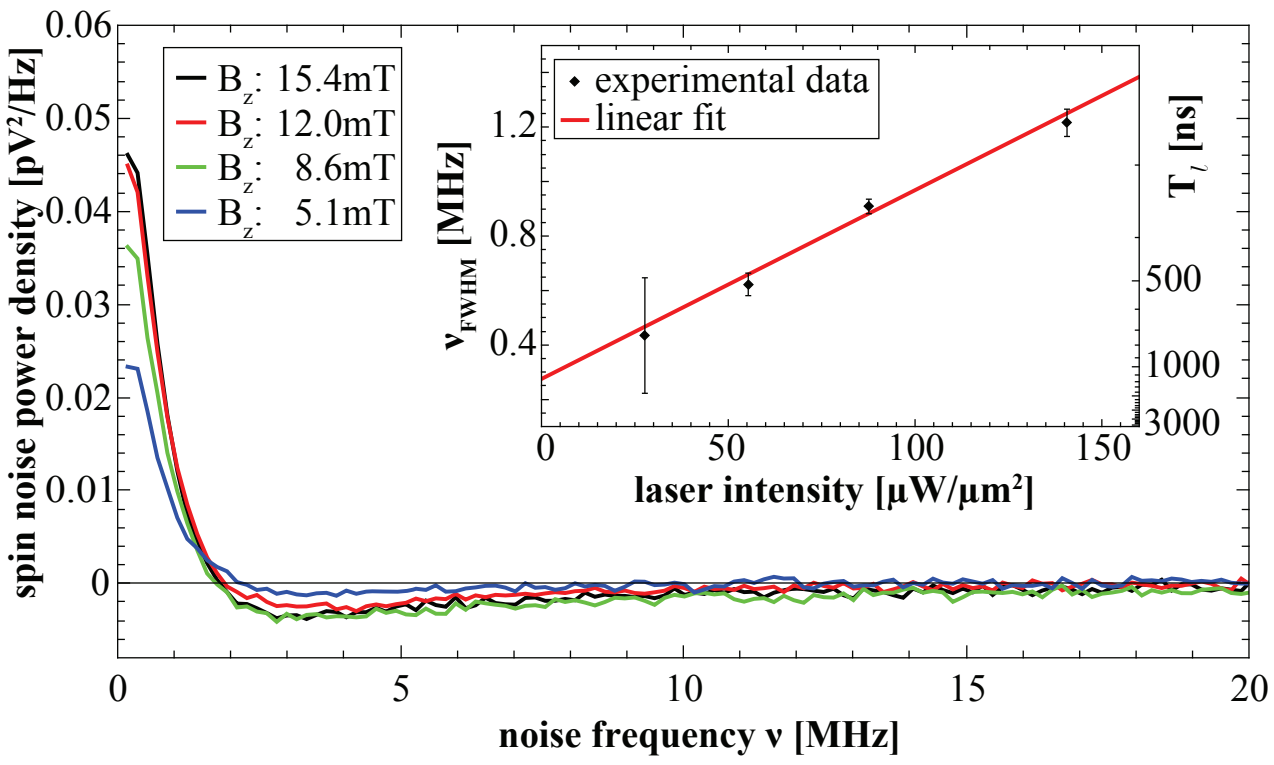

FIG. 3: (Color online) Spin noise difference spectra at $B_z^{ext} =$ 5.1 mT (blue), 8.6 mT (green), 12 mT (red), and 15.4 mT (black) minus $B_z^{ext} = 0$ mT. (Inset) Intensity dependence of the narrow SN peak ($1/(\pi\tau_{slow}^{hh})$) for $B_z^{ext} = 30$ mT.

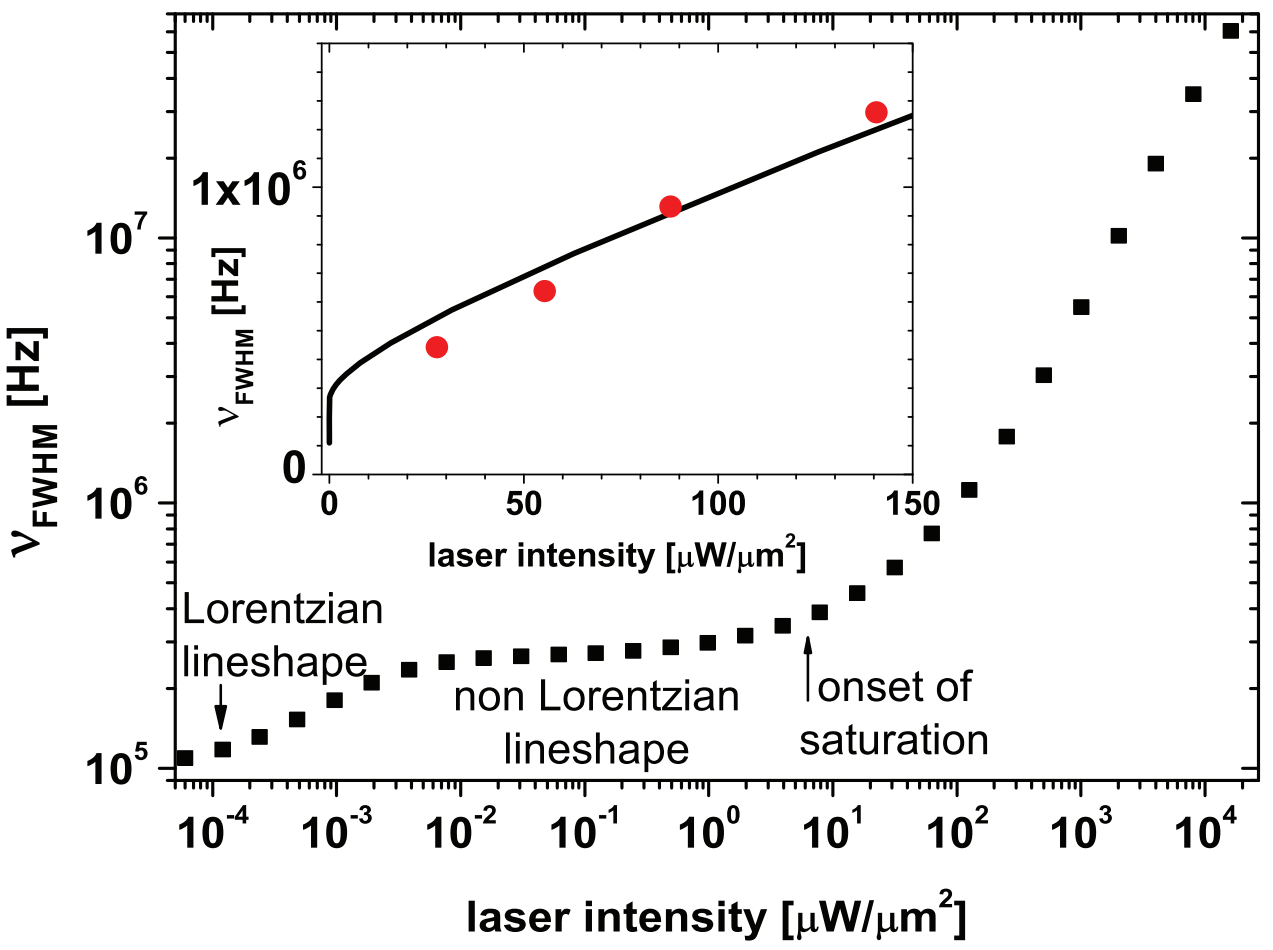

FIG. 4: (Color online) Calculated FWHM of the SN power in dependence on laser intensity for a hypothetic $\gamma_{I=0} = 10^5$ Hz ($\cong \tau_{slow}^{hh} \approx 31\ \mu$s) at zero laser intensity. (Inset) Comparison of calculated (black line) and measured (red dots) FWHM. The probability of light absorption by a single QD at resonant excitation is not exactly known in our microcavity sample and set as adjustable parameter to $1/6 \cdot 10^{-3}$.

nuclear magnetic field by measuring a SN spectrum at $B_{x,z}^{ext} = 0$ mT minus a SN spectrum at a transverse external magnetic field B_x^{ext}. A high transverse magnetic field [12] of $B_x^{ext} = 18$ mT shifts the complete SN power out of the detection window, i.e., the difference spectrum only includes the SN power at $B_{x,z}^{ext} = 0$ mT. The broad T_2^* SN spectrum is in this configuration less clearly visible since the narrow, longitudinal (T_l) and the broad transverse (T_2^*) SN peaks have the same sign. For $B_x^{ext} = 6$ mT, we measure only about half the amplitude of the longitudinal SN at $B_{x,z}^{ext} = 0$ mT since the total magnetic field is tilted in average by 45° with respect to the z-axis if $B_x^{ext} = B_z^N$. The tilting reduces the observed T_l spin noise power by a factor of two since the projection of the HH spins pointing along the tilted magnetic field on the z-direction is $1/\sqrt{2}$. The T_l SN measurements with transverse magnetic fields thereby confirm the amplitude of B^N which has been extracted from T_2^* measured with longitudinal magnetic fields. We want to point out that a tilted magnetic field reveals in SNS in general T_l and T_2^* at the same time, the first as a SN spectrum at $\nu = 0$ and the second shifted by the Larmor frequency.

Next, we want to demonstrate that the measured τ_{slow}^{hh} is not the intrinsic longitudinal spin relaxation time but significantly altered by light absorption. Spin noise spectroscopy can be in principle a non-demolition technique but our QD measurements reveal a clear intensity dependence for τ_{slow}^{hh}. The inset in Fig. 3 shows that the FWHM of the narrow peak at $B_z^{ext} = 30$ mT decreases almost linearly with decreasing excitation intensity. A linear extrapolation to zero intensity might be tempting but the intensity dependent broadening of the SN spectrum is different for each QD due to the different detunings of the laser frequency from the individual QD resonances. The dependence of the integrated SN spectrum of the QD ensemble on the intensity I can be calculated by

$$\int_0^{+\infty} G(E,I) \cdot n^2(E) \cdot R(E,I) \cdot L(\gamma(E,I))dE \tag{1}$$

where $G(E)$ is the Gaussian energy distribution of the QDs ground state resonance with a measured FWHM of 30 meV, n is the dispersive part of the QD refractive index at the laser frequency, $R(E,I) = 1 - \alpha(E,I)\tau_{PL}$ includes that optically excited QDs with the radiative lifetime τ_{PL} do not contribute to the HH SN spectrum due to Pauli blockade of the heavy holes, and L is the Lorentzian SN spectrum of a single QD with a FWHM $\gamma(E,I) = \gamma_{I=0} + \alpha(E,I)/\pi$ where $\gamma_{I=0} = 10^5$ Hz and $\alpha(E,I)$ is the number of absorbed photons per second. The calculated ν_{FWHM} is depicted in Fig. 4 and reveals three distinct intensity regimes. A moderate increase of ν_{FWHM} at extremely low laser intensities due to excitation of nearly resonant QDs, a weak increase at intermediate intensities, and a strong increase for very high intensities where all QDs are strongly excited. A comparison with our experimental data (red dots in the inset of Fig. 4) shows, firstly, the good agreement between calculations and experiment, secondly, that the laser intensities of our experiment coincide with the high intensity limit from which a linear extrapolation to zero intensity is not justified, and, thirdly, that the intensity dependent broadening is significant for T_l but not for T_2^*. At first sight, the calculations might imply that T_l measurements on single QDs by SN are experimentally impractical, however, the relative SN power around $\nu = 0$ increases significantly with decreasing laser intensity since quasi-resonant QDs are only weakly perturbed and thereby contribute strongly.[13]

In conclusion, we have measured in a quantum dot ensemble the T_l and T_2^* heavy hole spin relaxation times by spin noise spectroscopy. The T_2^* time and the transverse magnetic field dependence both yield a heavy hole hyperfine interaction with an effective stochastic nuclear magnetic field $B_N \approx 6$ mT. Intensity dependent measurements and calculations show that the very long T_l heavy hole spin relaxation time is significantly influenced by laser excitation and that a linear extrapolation to zero intensity is not justifiable.

We gratefully acknowledge the excellent technical support by R. Hüther and financial support by the BMBF joint research project *QuaHL-Rep*, the Deutsche Forschungsgemeinschaft in the framework of the priority program "SPP 1285 - Semiconductor Spintronics" and the excellence cluster "QUEST - Center for Quantum Engineering and Space-Time Research".

---

[1] B. Eble, C. Testelin, P. Desfonds, F. Bernardot, A. Balocchi, T. Amand, A. Miard, A. Lemaître, X. Marie, and M. Chamarro, Phys. Rev. Lett. **102**, 146601 (2009).

[2] J. Fischer, W. A. Coish, D. V. Bulaev, and D. Loss, Phys. Rev. B **78**, 155329 (2008).

[3] P. Fallahi, S. T. Yılmaz, and A. Imamoğlu, Phys. Rev. Lett. **105**, 257402 (2010).

[4] B. D. Gerardot, D. Brunner, P. Dalgarno, P. Öhberg, S. Seidl, M. Kroner, K. Karrai, N. G. Stoltz, P. M. Petroff, and R. J. Warburton, Nature **451**, 441 (2008).

[5] D. Brunner, B. D. Gerardot, P. A. Dalgarno, G. Wüst, K. Karrai, N. G. Stoltz, P. M. Petroff, and R. J. Warburton, Science **325**, 70 (2009).

[6] M. Oestreich, M. Römer, R. J. Haug, and D. Hägele, Phys. Rev. Lett. **95**, 216603 (2005).

[7] G. M. Müller, M. Römer, D. Schuh, W. Wegscheider, J. Hübner, and M. Oestreich, Phys. Rev. Lett. **101**, 206601 (2008).

[8] G. M. Müller, M. Oestreich, M. Römer, and J. Hübner, Physica E **43**, 569 (2010).

[9] S. A. Crooker, J. Brandt, C. Sandfort, A. Greilich, D. R. Yakovlev, D. Reuter, A. D. Wieck, and M. Bayer, Phys. Rev. Lett. **104**, 036601 (2010).

[10] M. Bayer, G. Ortner, O. Stern, A. Kuther, A. A. Gorbunov, A. Forchel, P. Hawrylak, S. Fafard, K. Hinzer, T. L. Reinecke, S. N. Walck, J. P. Reithmaier, F. Klopf, and F. Schäfer, Phys. Rev. B **65**, 195315 (2002).

[11] The equation $\nu_{\mathrm{FWHM}} = 1/(\pi\tau)$ is strictly valid only for a Lorentzian line shape.

[12] Note that $\mu_B B \ll k_B T$. Thereby, magnetic field induced hole spin polarization is negligible small.

[13] At very low laser intensities, the electrical noise of our 80 MHz New Focus balanced receiver becomes much larger than the optical shot noise, i.e., an optimized low noise (low frequency) balanced receiver would be advantageous for single QD SN spectroscopy.